

The Effect of Thermal Treatment of Birch Wood on the Cutting Power of Plain Milling

Monika Kvietková

This article deals with cutting power during the plane milling of thermally treated and untreated silver birch (*Betula pendula* Roth.) wood. Thermal treatment was carried out at various temperatures of 160, 180, 210, and 240 °C. The cutting power was measured under various milling conditions, such as rake angle of tool (10°, 15°, 20°, 25°, and 30°), cutting speed (20, 40, and 60 m/s), and feed speed (4, 8, and 11 m/min). Thermal treatment had no clear impact on the cutting power. Treated wood at 160 and 180 °C had lower values of cutting power in comparison with untreated wood, while the opposite trend was observed at 210 and 240 °C. The results show that with increasing speed feed, there is an increase in cutting power, while the opposite effect was achieved by changing the cutting speed. The optimum values of cutting power were achieved at a 10° angle and a thermal treatment of 160 °C.

Keywords: Cutting power; Plane milling; Thermally modified wood; Cutting speed; Feed speed; Rake angle; Treatment temperature

Contact information: Department of Wood Processing, Faculty of Forestry and Wood Sciences, Czech University of Life Sciences in Prague, Kamýcká 1176, Praha 6 - Suchbátka, 16521 Czech Republic;

** Corresponding author: monikakvietkova@gmail.com*

INTRODUCTION

Price and quality are the basic criteria according to which a given product is evaluated, not only for manufacturers, but also for the consumer. In general, a lower price is more desirable. For manufacturers, a lower price indicates easier and faster production.

Knowledge of the cutting power or overall power consumption for a given machine type is crucial for the determination of production costs. The goal of each producer is to reduce the cost of production to a minimum, so even this partial expense (the energy consumption of the machinery) has an impact on the overall value of the product. Therefore, the appropriate selection of cutting tool material, angular geometry of the cutting edge, and optimum cutting conditions, help to reduce these costs. Cutting power is an important parameter for machinery, mostly in terms of energy intensity,

lignin, and hemicellulose thermal degradation because of elevated temperatures in the range of 150 to 260 °C (Kačíková and Kačík 2011).

Thermally modified wood is easier to machine (both manually and mechanically) and has smoother cut areas (Kvietková *et al.* 2015b) because of the decrease in strength caused by higher temperatures. A potential problem is the generation of fine dust, which must be trapped in special filters to prevent the contamination of the working environment and health problems of the operators, and eventually dust inhalation. Milling is undoubtedly one of the most frequently used processing methods. Milling is a type of chip machining method (Vasilko 2007). The chip thickness ranges from zero to certain maximum values. Chip thickness below a certain value reduces the milling cutter yield capacity and causes premature wear of the blade. The maximum chip thickness is determined by the protuberance of the cutting blade from the cutting head.

Milling is based on the gradual removal of the machined piece material by a multi-wedge tool. This removal method utilizes a form of chip, and the main movement is rotation performed by the tool (milling cutter). The feeding movement is carried out by either the piece or the tool, usually in the direction perpendicular to the tool axis. Usually, the milling cutters are tools with various cutting edges of many shapes rotating around their axes during the operation, as opposed to cutting the chips with their cutting edges by the mutual shift of the tool against the piece (Lisičan 1996). Efficient milling processes can be carried out only under a predetermined machining condition. These conditions are mainly related to the correct determination of the cutting speed with respect to the type of tool, feed per tooth, workpiece quality, and durability of the blade (Kocman and Prokop 2001).

This work focused on the influence of thermal treatment and various parameters on cutting power during the plane milling of birch wood. Thermal treatment was carried out at four temperatures (160, 180, 210, and 240 °C), and the results were compared with those of untreated wood. Milling was carried out at cutting speeds of 20, 40, and 60 m/s, feed speeds of 4, 8, and 11 m/min, and with tool rake angles of 10°, 15°, 20°, 25°, and 30°.

EXPERIMENTAL

Materials

Fifty-five-year-old silver birch (*Betula pendula* Roth.) trees harvested from the central region of the Czech Republic, near Kostelec nad Černými lesy, were used in this study. The zones selected for sample preparation were cut from the middle parts, between the pith and bark. Samples, without defects, with dimensions of 40 mm × 100 mm × 500

Procedure

Thermal treatment

Birch samples were placed on a metal grate and subsequently placed into the thermal chamber model S400/03 (LAC Ltd., Czech Republic). The thermal treatment was carried out under specific conditions in three phases (Tables 1 and 2) for each final temperature according to ThermoWood® process developed by VTT, Finland.

Table 1. Thermal Treatment

Thermal Treatment	Description
I. Phase	Drying and simultaneous heating of the wood to the desired final temperatures of 160, 180, 210, and 240 °C using steam as a protective vapor.
II. Phase	The desired temperature maintained for the specified time (5h).
III. Phase	Cooling the chamber and wood samples to 40 °C. The wood was re-moisturized in order to achieve the end-use moisture (5 to 7 %).

Table 2. Duration of Thermal Treatment

Required Final Temperature (°C)	Thermal Treatment			
	I. Phase (h)	II. Phase (h)	III. Phase (h)	Total Time (h)
160	4.0	5.0	2.0	11.0
180	5.0	5.0	2.5	12.5
210	6.0	5.0	3.0	14.0
240	7.0	5.0	3.5	15.5

After thermal treatment, the samples were conditioned ($\phi = 65 \pm 3\%$ and $t = 20 \pm 2$ °C) for three weeks. Before experiments, all samples were machined to their final thickness (25 mm) using a DHM 630P thickness planer (Holzmann, Germany). Native and thermally-modified samples with final dimensions of 25 mm × 100 mm × 500 mm were prepared for the plane milling process. Thermal treatment was carried out in the same manner as in previous work by Kvietková *et al.* (2015a, b).

Plane milling

Peripheral plane milling was carried out using a one-spindle lower cutter FVS 3470 (Ligmet, Czech Republic) with an STEFF 2034 feeding system (Maggi Technology, Italy). Two-blade cutter heads (ϕ 130 mm) with five types of exchangeable knives (at

Cutting power measurement

The power consumption was recorded using a digital power meter MI 2392 PowerQ Plus (Metrel d.d., Slovenia), both in idling and cutting conditions, and subsequently processed in a computer using software PowerQ Link 2.1. The measured values, recorded within 1-s intervals (1024 values measured per second) were then averaged. Average cutting power was the value of the complete electrical cutting power corrected by the idling power.

Evaluation and Calculation

The influence of the investigated factors on cutting power was statistically evaluated using analysis of variance (ANOVA), primarily by Fisher's F-test, using Statistica 12 software (Statsoft Inc., USA).

The density of the wood before and after treatment was calculated according to ISO 13061-2 2014 and Eq. 1,

$$\rho_w = \frac{m_w}{a_w * b_w * l_w} = \frac{m_w}{V_w} \quad (1)$$

where ρ_w is the density of the test sample at a certain moisture content w (kg/m^3); m_w is the mass (weight) of the test sample at a certain moisture content w (kg); a_w , b_w , and l_w are the dimensions of the test sample at a certain moisture content w (m); and V_w is the volume of the test sample at a certain moisture content w (m^3).

The moisture content of the samples was determined according to ISO 13061-1 (2014) and Eq. 2,

$$w = \frac{m_w - m_0}{m_0} * 100 \quad (2)$$

where w is the moisture content of the sample (%); m_w is the mass (weight) of the test sample at a certain moisture content w (kg); and m_0 is the mass (weight) of the oven-dry test sample (kg).

Drying to an oven-dry state was also carried out according to ISO 13061-1 (2014).

RESULTS AND DISCUSSION

Table 4 contains a statistical evaluation of both the impact of the individual factors and the simultaneous interaction of all the factors. Based on the significance level

increased brittleness, and therefore its resistance to the penetration of tool is lower. Probable cause nearly the same cutting power can be found in our milling conditions, it was used because of a constant feed speed as well as the cutting depth. This caused that the effect of increasing cutting speed was subdued.

Table 4. Effect of Factors on Cutting Power According to ANOVA Analysis

Monitored Factor	Sum of Squares	Degrees of Freedom	Variance	Fisher's F-Test	Significance Level P
Intercept	482927452	1	482927452	654101.3	0.001
Cutting speed	6104	2	3052	4.1	0.016
Feed speed	130176	2	65088	88.2	0.001
Treatment temperature	3261989	4	815497	1104.6	0.001
Rake angle	17400975	4	4350244	5892.2	0.001
Cutting speed × Feed speed × Rake angle × Treatment temperature	880124	64	13752	18.6	0.001
Error	996714.28	1350	738.30		

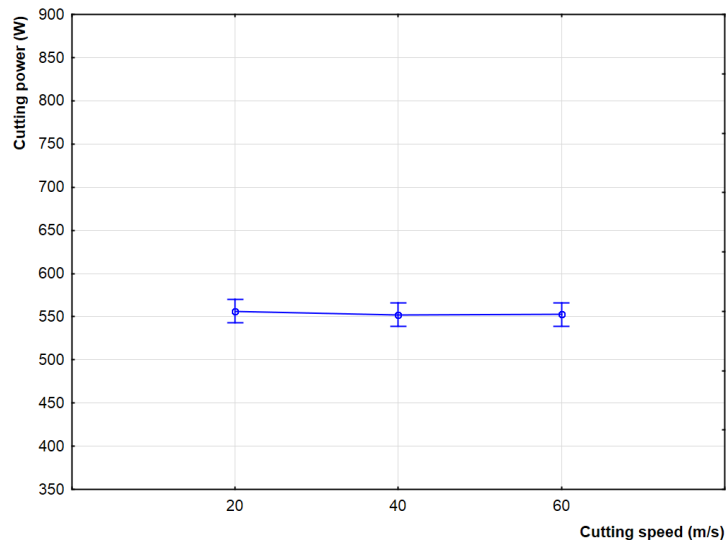


Fig. 1. 95% confidence interval showing the influence of cutting speed on cutting power

The data in Fig. 2 show that increasing the rake angle equally increased the cutting power up to 25°, after which the cutting power decreased. In general, the increase

cutting power value. This well-known fact has also been confirmed by other authors such as Marthy and Cismaru (2009), Barcık *et al.* (2010), Mandić *et al.* (2010), and Răcășan and Ispas (2015).

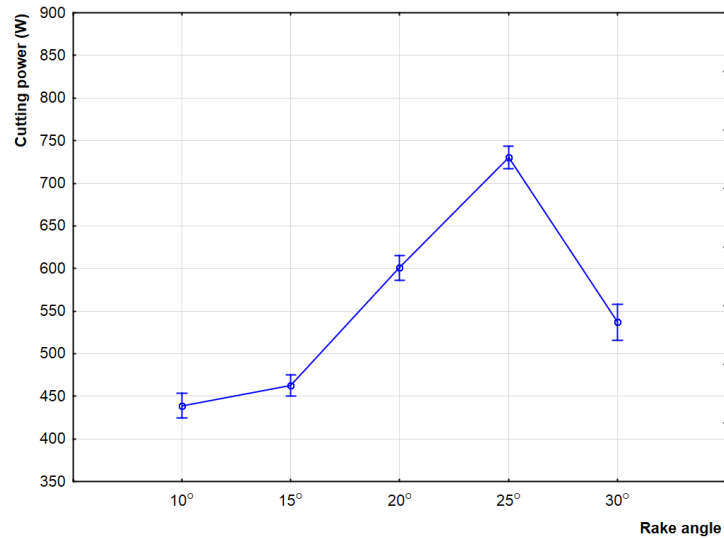


Fig. 2. 95% confidence interval showing the influence of rake angle on cutting power

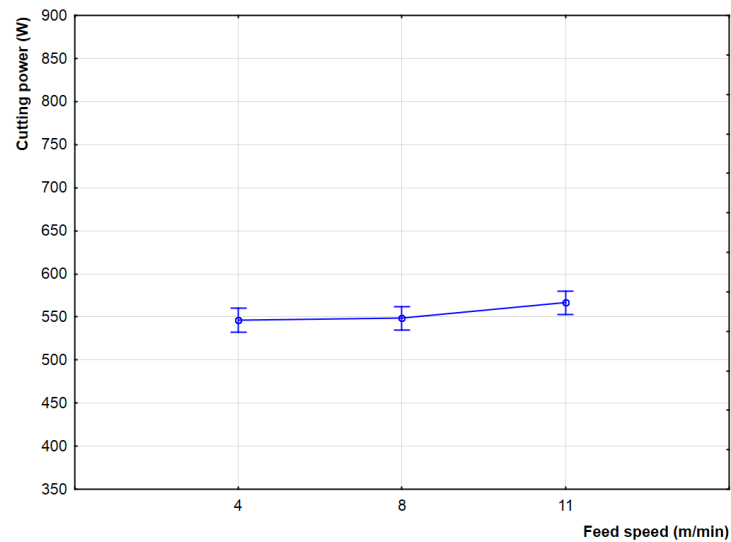


Fig. 3. 95% confidence interval showing the influence of feed speed on cutting power

(Mandić *et al.* 2010; Kollmann and Cote 2012). This fact confirms the results of authors such as Wilkowski *et al.* (2011) and Mandić *et al.* (2010). For example, Kivimaa (1950) found a local maximum of the cutting power at moisture content about 9%. Therefore, varying moisture content should be a probable cause of differences in cutting power for wood modified at various temperatures. It would be interesting to study how the moisture is distributed during milling of thermally treated wood at different temperatures.

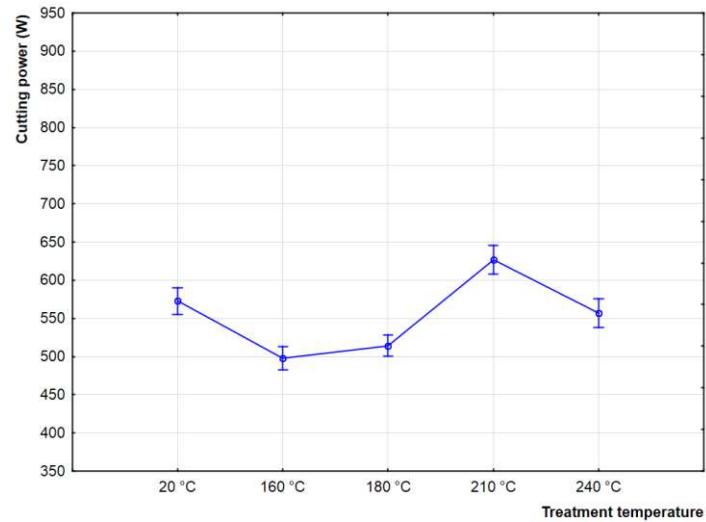
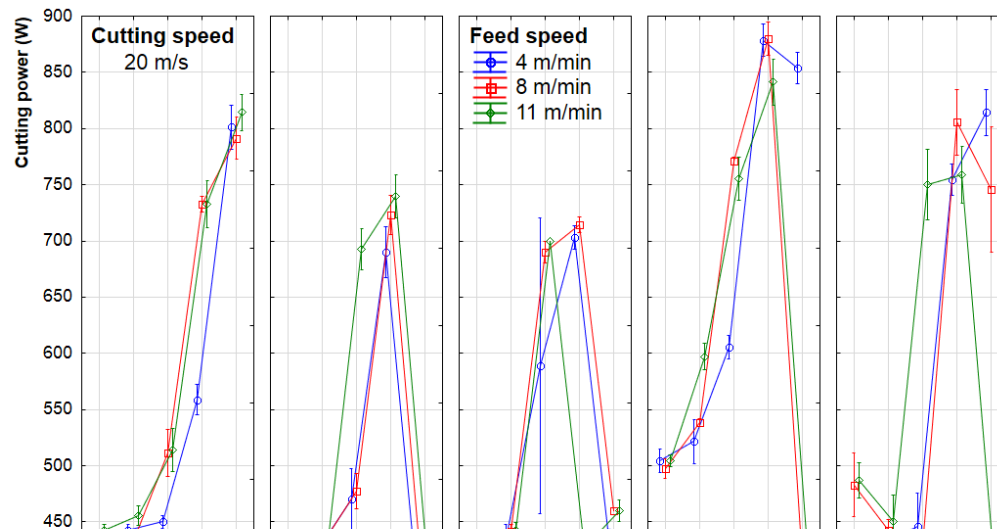


Fig. 4. 95% confidence interval showing the influence of treatment temp on cutting power




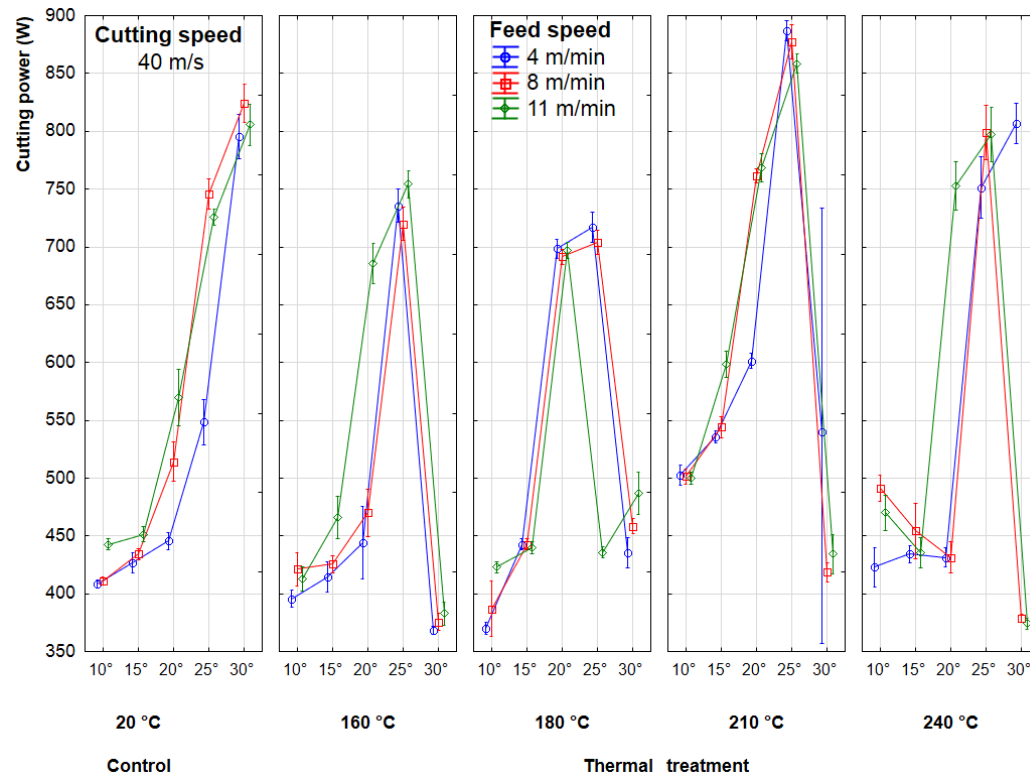


Fig. 6. 95% confidence interval showing the influence of treatment temperature, feed speed, and rake angle on cutting power at a cutting speed of 40 m/s

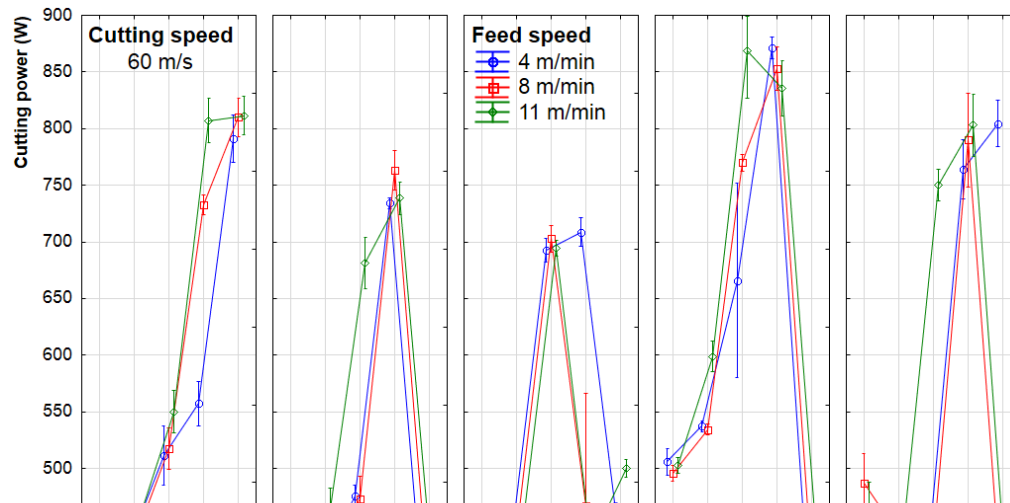

Figures 5 to 7 show the effects of all factors on the cutting power for individual cutting speeds of 20, 40, and 60 m/s. As can be seen from the individual curves, it is difficult to determine the definitive manner of the cutting power, depending on the examined factors. Thermally modified birch wood achieved an increase in cutting power due to the increase in feed speed and rake angle, while cutting speed had the least significant effect. Thermally modified wood had a similar nature at individual temperatures, and even at the individual factors.

CONCLUSIONS

1. Thermal treatment had an important influence on cutting power during the plane milling of birch wood but its manner was ambiguous.
2. The highest values of cutting power during the plane milling of thermally modified birch wood were achieved when using a tool with a rake angle of 25° while at unmodified wood the highest values were achieved when using a tool with a rake angle of 30°. In general, rake angles of 10° and 15° yielded the lowest values of cutting power, but in some case, the lowest values were achieved at 30°.
3. There was an increase in the cutting power of plane milling when the feed speed was increased.
4. An increase in the cutting speed had a statistically significant influence on the cutting power, although the differences between individual cutting speeds were small.

ACKNOWLEDGMENTS

The paper was partially supported by grant of the Ministry of Agriculture of the Czech Republic, NAZV, No. QJ 1330233 and also by project of the Internal Grant Agency of the Faculty of Forestry and Wood Sciences, No. B05/15.

REFERENCES CITED

- Barčík, Š., and Gašparík, M. (2014). "Effect of tool and milling parameters on the size distribution of splinters of planed native and thermally modified beech wood," *BioResources* 9(1), 1346-1360. DOI: 10.15376/biores.9.1.1346-1360
- Barčík, Š., Kmiňák, P., ěbábek, T., and Kvietková, M. (2010). "The influence of selected

- Goglia, V. (1994). *Strojevi i alati za obradu drva I. [Machines and Tools for Woodworking I.]*, Šumarski fakultet Sveučilište u Zagrebu, Zagreb, Croatia (in Croatian).
- Gündüz, G., Korkut, S., and Korkut, D. S. (2008). “The effects of heat treatment on physical and technological properties and surface roughness of Camiyani black pine (*Pinus nigra* Arn. subsp. *pallasiana* var. *pallasiana*) wood,” *Bioresource Technology* 99(7), 2275-2280. DOI: 10.1016/j.biortech.2007.05.015
- ISO 13061-1 (2014). “Physical and mechanical properties of wood -- Test methods for small clear wood specimens -- Part 1: Determination of moisture content for physical and mechanical tests,” International Organization for Standardization, Geneva, Switzerland.
- ISO 13061-2 (2014). “Physical and mechanical properties of wood -- Test methods for small clear wood specimens -- Part 2: Determination of density for physical and mechanical tests,” International Organization for Standardization, Geneva, Switzerland.
- Kačíková, D., and Kačík, F. (2011). *Chemické a mechanické zmeny dreva pri termickej úprave [Chemical and mechanical changes during thermal treatment of wood]*, Technical University in Zvolen, (in Slovak).
- Kivimaa, E. (1950). *Cutting forces in woodworking*, State Institute for Technical Research, Helsinki, Finland, 102 p.
- Kocman, K., and Prokop, J. (2001). *Technologie obrábění (Technology of Machining)*. 1. ed., CERM, Brno, Czech Republic (in Czech).
- Kollmann, F. F. P., and Cote Jr., W. A. (2012). *Principles of Wood Science and Technology I: Solid Wood*. Softcover reprint of the original 1st Ed. 1968, Springer-Verlag, Berlin.
- Kvietková, M., Gaff, M., Gašparík, M., Kaplan, L., and Barčík, Š. (2015a). “Surface quality of milled birch wood after thermal treatment at various temperatures,” *BioResources* 10(4), 6512-6521. DOI: 10.15376/biores.10.4.6512-6521
- Kvietková, M., Gašparík, M., and Gaff, M. (2015b). “Effect of thermal treatment on surface quality of beech wood after plane milling,” *BioResources* 10(3), 4226-4238. DOI: 10.15376/biores.10.3.4226-4238
- Liščan, J. (1996). *Teória a Technika Spracovania Dreva [Theory and Technique of Wood Processing]* Matcentrum, Zvolen, Slovakia (in Slovak).
- Mandić, M., Todorović, N., Popadic, R., and Danon, G. (2010). “Impact of thermal modification and technological parameters of processing on cutting powers in milling wood processing,” *Proceedings of the First Serbian Forestry Congress – Future with Forests*, 11–13th November, Belgrade, Serbia, pp. 1438-1453.
- Marthy, M., and Cismaru, I. (2009). “Experimental study concerning the power

Vasilko, K. (2007). *Analytická Teória Trieskového Obrábania [Analytical Theory of Chip Machining]* 1st Ed., Fakulta Výrobných Technológií v Košiciach, Prešov, Slovakia (in Slovak).

Wilkowski, J., Grzeškiewicz, M., Czarniak, P., Siwek, I., Javorek, L., and Paulíny, D. (2011). "Influence of thermal modification of oak wood on cutting forces during milling," *Annals of Warsaw University of Life Sciences – SGGW, Forestry and Wood Technology* 76(1), 203-207.

Article submitted: July 31, 2015; Peer review completed: September 20, 2015; Revised version received: September 22, 2015; Accepted: October 13, 2015; Published: November 3, 2015.

DOI: 10.15376/biores.10.4.8528-8538

